

Chief	Tester	Date	Data No.
鍾招平		張雅屏 113.01.30	C4010037

Proposal

Material: A) 100% CDP 75D/72F (T&T)
 B) 88% CDP 100D/144F + OP 12% (T&T)


Process: A) Dyeing (120°C X 30')
 B) Dyeing (120°C X 50')

Recipe: Pantone 13-1023

A)

Taiacryl Yellow AD-RST 0.139%
 Taiacryl Red AD-2GLT 0.027%

PH4

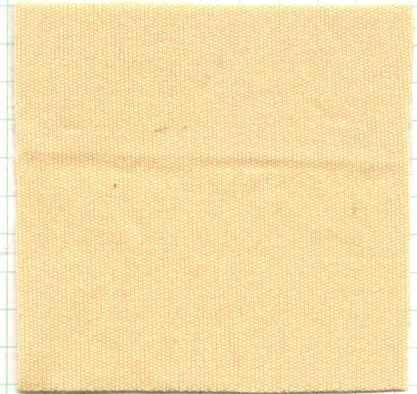

Washing Fastness Test(AATCC2A)

Before After

T&T MIX A)




Pantone 13-1023

B)

Taiacryl Yellow AD-RST 0.122%
 Taiacryl Yellow AD-3RLT 0.014%
 Taiacryl Red AD-2GLT 0.0242%

PH4

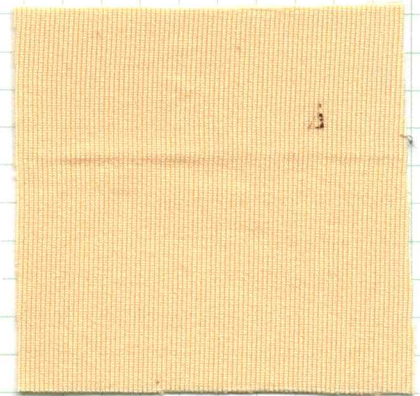

Washing Fastness Test(AATCC2A)

Before After

T&T MIX B)



T & T INDUSTRIES CORPORATION

NO 3.KUO-CHIEN 1ST RD.KUAN-YIN IND. ZONE, TEL : (03)4831666

TAO-YUAN HSIEN, TAIWAN

FAX : (03)4832666

Standard Name 275 of 283

PANTONE 13-1023 (C4010037)

Instrument Setup: %R USAV SCI UV Inc

Batch Name 24 of 26


CDP+OP Mix A

Date: 29-Jan-24 Time: 13:32:46


Instrument Setup: %R LAV SCI UV Inc

CMC DE Pass/Fail Tolerance: 0.50

l:c Ratio: (2.00 1.00)

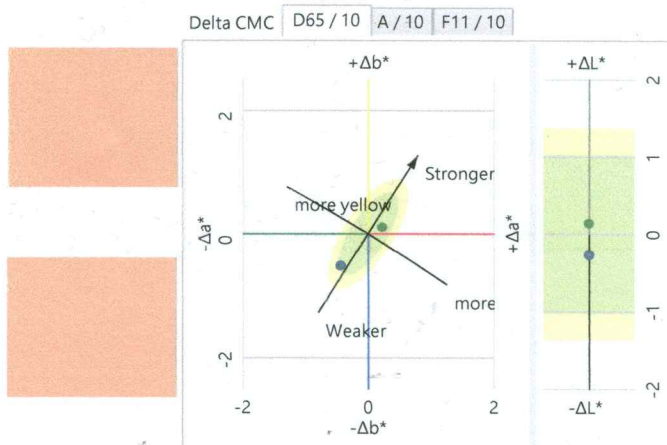

Batch Name	III/Obs	DL*	Da*	Db*	CIE DE	DL*/ISL	DC*/cSC	DH*/SH	CMC DE	Status	Strength
CDP 100% Mix A	D65 10 Deg	0.14	0.22	0.11	0.28	0.05	0.10	-0.16	0.20	Pass	98.22
CDP 100% Mix A	A 10 Deg	0.16	0.39	0.73	0.85	0.06	0.37	0.04	0.37	Pass	
CDP 100% Mix A	F11 10 Deg	0.43	0.63	0.01	0.76	0.15	0.15	-0.63	0.66	Fail	
CDP+OP Mix A	D65 10 Deg	-0.28	-0.44	-0.52	0.73	-0.10	-0.32	0.13	0.36	Pass	99.28
CDP+OP Mix A	A 10 Deg	-0.36	-0.18	-0.17	0.44	-0.13	-0.10	0.08	0.19	Pass	
CDP+OP Mix A	F11 10 Deg	-0.04	0.03	-0.64	0.64	-0.02	-0.25	-0.39	0.47	Warn	

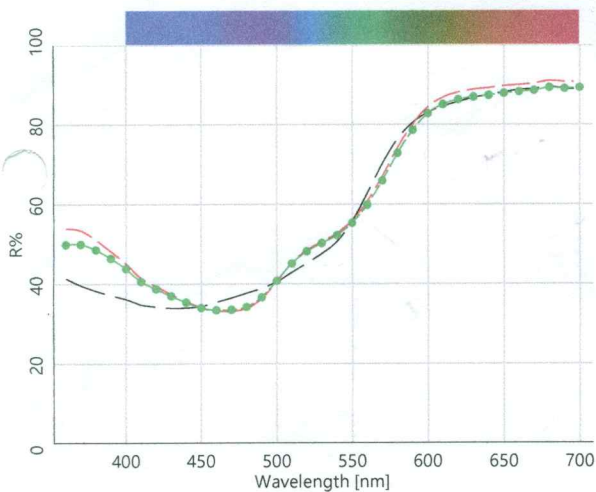

———— PANTONE 13-1023 (C4010037)

----- CDP+OP Mix A

Batch Name

CDP 100% Mix A
CDP 100% Mix A
CDP 100% Mix A

CDP+OP Mix A
CDP+OP Mix A
CDP+OP Mix A

Metamerism

lighter
0.63 lighter
0.51 lighter

darker
0.47 darker
0.55 darker

Color Comments

more red more yellow
more red more yellow
more red more yellow

more green more blue
more green more blue
more red more blue